

## SHORT COMMUNICATIONS

## MEASUREMENT OF CORROSION RATE AND DOUBLE-LAYER CAPACITY BY LARGE AMPLITUDE EXPONENTIAL RELAXATION TECHNIQUE

V. LAKSHMINARAYANAN and S. R. RAJAGOPALAN\*

*Raman Research Institute, Bangalore 560 080, India.**\* Materials Science Division, National Aeronautical Laboratory, Bangalore 560 017, India.*

PRABHAKARA Rao and Rangarajan<sup>1</sup> have shown that the potential-time ( $\eta - t$ ) transient obtained by impressing an exponentially decaying current of sufficiently large magnitude to an electrochemical system corresponds to an accelerated Tafel plot. They applied this technique to the system, hydroquinone-quinone/Pt and demonstrated that this method can be successfully used for the determination of kinetic parameters. This technique was applied to corrosion rate ( $i_{\text{corr}}$ ) measurement by Prabhakara Rao and Yegnaraman<sup>2</sup>. However, their results showed that the measured  $i_{\text{corr}}$  was dependent on  $\tau$ .

In this communication we show that this method can be used to measure  $i_{\text{corr}}$ , Tafel slopes and  $C_d(E)$  of the corrosion systems under activation control.

When a current input of the form  $\Delta I \exp(-t/\tau)$ , where  $\Delta I$  is sufficiently large to keep the system in the Tafel region, is applied to a corrosion system under activation control, the resulting current-potential relationship can be shown to be,

$$i = \Delta I \exp(-t/\tau) = -C_d \frac{d\eta}{dt} + i_{\text{corr}} \exp(-2.303\eta/b_c) \quad (1)$$

or

$$i = \Delta I \exp(-t/\tau) = -C_d \frac{d\eta}{dt} - i_{\text{corr}} \exp(2.303\eta/b_a), \quad (2)$$

where  $b_c$  and  $b_a$  are Tafel slopes of cathodic and anodic reactions of the corrosion system. If the charging current ( $= -C_d(d\eta/dt)$ ) is zero, then (1) and (2) become

Tafel relations. Under such conditions  $\eta - t$  transient will be a straight line and an accelerated Tafel plot is obtained. However, charging current is generally not negligible except when  $\tau$  is very large compared to the time required for charging the double layer. Even under conditions where double-layer charging current cannot be neglected, it can be easily corrected for corrosion systems under activation control by using the elegant approach suggested by Rangarajan<sup>1,3</sup>.

When charging and activation are both present,  $\eta - t$  transient exhibits a maximum. At  $t_{\text{max}}$ , the current is entirely faradaic because  $(d\eta/dt)$  is zero at that instant. Hence a Tafel plot uncorrupted by double-layer charging can easily be got by using the  $\eta_{\text{max}}$  and  $i$  at  $t_{\text{max}}$  of several transients obtained by varying  $\Delta I$  keeping  $\tau$  constant. Getting  $i_{\text{corr}}$ ,  $b_a$  and  $b_c$  from the Tafel plot is straightforward.

A second approach is to correct a single transient for double-layer charging by the procedure described below. At each  $\eta$  value, the total current is equal to the sum of faradaic current ( $i_F$ ) and non-faradaic current ( $i_{nF}$ ). For every  $\eta$  (excepting  $\eta_{\text{max}}$ ) there are two values of current; one in the rising portion ( $i_{11}$ ) and another in the falling portion ( $i_{12}$ ). However,  $i_F$  will be the same both in the rising and falling portions at constant  $\eta$ . Therefore it is easy to show that

$$(i_F)_{11} = (i_{11}) + C_d(d\eta/dt)_{11}, \quad (3)$$

$$\text{where } C_d = \frac{(i_{12}) - (i_{11})}{(d\eta/dt)_{11} - (d\eta/dt)_{12}}. \quad (4)^*$$

At each  $\eta$ ,  $i_F$  can be calculated by (3). By plotting these values of  $i_F$  against the corresponding values of  $\eta$  in the semilog paper,  $i_{\text{corr}}$  and Tafel slopes can be found. Incidentally,  $C_d = f(E)$  is recovered from (4).

Employing the system, mildsteel in 1N sulphuric acid (deaerated) and using a measurement set up consisting of galvanostat and transient data recorder<sup>4</sup> the conclusions drawn above were verified.

The values of  $i_{\text{corr}}$  obtained after correcting for charging current by multitransient and single transient methods are shown in table 1 and are in good agreement with the steady-state logarithmic polarization value. It is clear from the present result that double-layer charging current correction leads to the measurement of true corrosion rate. No variation of

\*Ref. 6 gives a similar equation in a different context.

Table 1  $i_{\text{corr}}$  of MS in 1N  $\text{H}_2\text{SO}_4$  (deaerated) obtained at various  $\tau$  values after correcting for double-layer charging current

	$\tau$ (m sec)	$i_{\text{corr}}$ cathodic polarization (mA/cm <sup>2</sup> )	$i_{\text{corr}}$ anodic polarization (mA/cm <sup>2</sup> )	$b_c$ (mV)	$b_a$ (mV)
Method 1 (by using $\eta_{\text{max}}$ and $i$ at $t_{\text{max}}$ ; multitransient method)	1	1.45	1.30	93	76
	10	1.40	1.35	96	83
	100	1.40	1.35	99	83
	500	1.40	1.30	99	76
	1000	1.35	1.35	99	83
Method 2 (using single transient corrected for double-layer charging)	5	1.40	1.40	103	83
	7.5	1.50	1.40	103	86
	10	1.40	1.45	96	86
	50	1.40	1.40	96	83

Note: Steady-state logarithmic polarization data  $i_{\text{corr}}$  (from cathodic and anodic Tafel plots) = 1.35 mA/cm<sup>2</sup>;  $b_c$  = 96.3 mV;  $b_a$  = 83 mV.

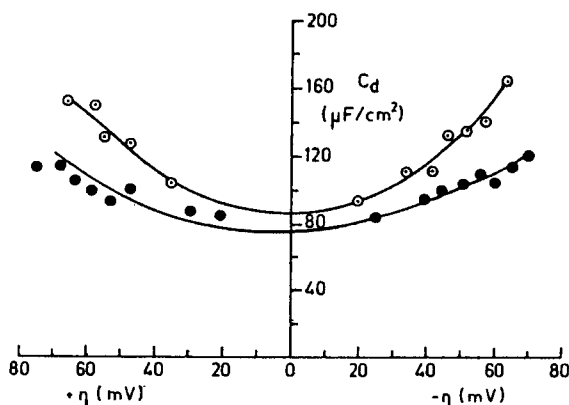


Figure 1. Variation of  $C_d$  with overpotential for MS in 1N  $\text{H}_2\text{SO}_4$  (deaerated) with and without hexamine inhibitor. ○ without inhibitor; ● with 10 mM hexamine inhibitor.

$i_{\text{corr}}$  with  $\tau$  is seen. Obviously, the results obtained by Prabhakara Rao and Yegnaraman<sup>2</sup> showed variation of  $i_{\text{corr}}$  with  $\tau$  essentially due to the neglect of double-layer charging current.

A plot of  $C_d$  vs  $\eta$  for MS in 1N  $\text{H}_2\text{SO}_4$  (deaerated) obtained from a single transient recorded at  $\tau = 50$  m sec is shown in figure 1. The effect of adding hexamine (10 mM) as inhibitor is also shown in the same figure. The decrease in double-layer capacity brought about by the adsorption of the inhibitor is evident from the plot.


The value of  $i_{\text{corr}}$  obtained with a single  $\eta-t$  transient at  $\tau = 50$  m sec with and without inhibitor is shown in table 2. The values obtained by the two methods show an excellent consistency.

Since  $C_d$  is proportional to area it is possible to measure changes in the area of corroding system with time by this technique. Figure 2(a) shows corrosion rate of MS in 1N  $\text{H}_2\text{SO}_4$  as a function of time. It is seen that the corrosion rate increases with time. A similar trend was reported by Mansfeld<sup>5</sup> for the system of iron in 1N  $\text{H}_2\text{SO}_4$ . We investigated to find out whether such an increase is due to change in area of the electrode with time. From figure 2(b) it can be seen that  $C_d$  increases by about 20% showing that the area changes only by 20% in 3 hr. However, the corrosion rate increases by nearly three times during the same period. From this it is evident that increase in corrosion rate cannot be solely attributed to increase in area.

The exponential relaxation which was called as accelerated Tafel plot by Rangarajan and Prabhakara Rao<sup>1</sup> can be considered as nonlinear relaxation technique as distinct from linear relaxation technique<sup>3</sup>. It has been demonstrated in this paper that the exponential nonlinear relaxation technique can be used for corrosion systems under activation control to get (i) corrosion rate and Tafel slopes (ii)  $C_d$  values as a function of potential and (iii) area changes with time of corrosion systems. It is shown that the correction for double-layer charging is essential to obtain true corrosion rate. Such a correction can be accomplished easily. Neglecting the charging current contribution could

**Table 2** Corrosion rates of MS in 1N H<sub>2</sub>SO<sub>4</sub> (deaerated) obtained from single and multitransient methods with and without hexamine inhibitor  $\tau = 50$  m sec

Concentration of hexamine (mM)	$I_{\text{corr}}$ (mA/cm <sup>2</sup> )			
	Single transient method		Multitransient method	
	Cathodic polarization	Anodic polarization	Cathodic polarization	Anodic polarization
0	1.393	1.428	1.428	1.428
10	0.385	0.385	0.385	0.400

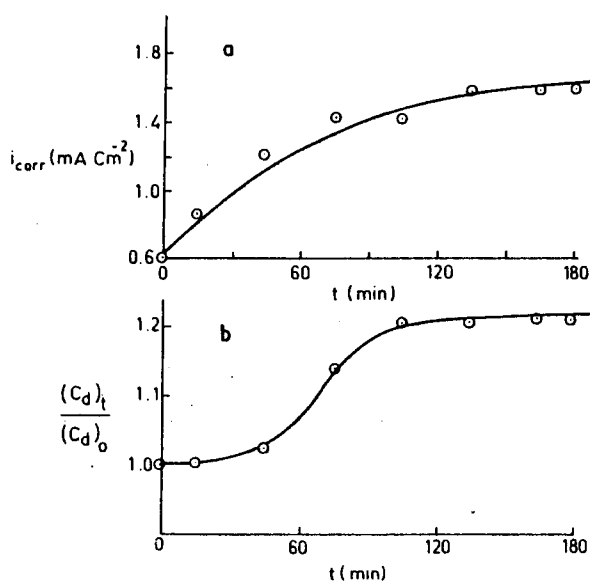

**Figure 2.** Time dependence of (a)  $i_{\text{corr}}$  and (b) area of the electrode.

5. Mansfeld, F., *J. Electrochem. Soc.*, 1973, **120**, 515.  
6. Rangarajan, S. K., *J. Electroanal. Chem.*, 1971, **32**, 329.

lead to such artefacts as variation of  $i_{\text{corr}}$  with time constant  $\tau$ .

15 April 1986

1. Prabhakara Rao, G. and Rangarajan, S. K., *J. Electroanal. Chem.*, 1974, **55**, 151.
2. Prabhakara Rao, G. and Yegnaraman, *Proc. Indian Natl. Sci. Acad.*, 1982, **A48**, 392.
3. Rangarajan, S. K., *J. Electroanal. Chem.*, 1973, **41**, 491.
4. Lakshminarayanan, V., Aithu Poojary and Rajagopalan, S. R., Unpublished results (1981).